



## The Effects of Liquid Butadiene Rubber and Resins as Processing Aids on the Physical Properties of SSBR/Silica Compounds

Muhammet Iz, Donghyuk Kim, Kiwon Hwang, Woong Kim,  
Gyeongchan Ryu, Sanghoon Song, and Wonho Kim<sup>†</sup>

*Department of Polymer Science & Chemical Engineering, Pusan National University, Busan 46241, Republic of Korea*

(Received October 12, 2020, Revised October 23, 2020, Accepted October 29, 2020)

**Abstract:** Highly aromatic (HA) oils are common processing aids used in tire tread compounds. However, they often bleed and evaporate from the vulcanizates during tire use. Thus, the mechanical and dynamical properties of the tire decrease. To overcome this problem, we investigated nonfunctionalized liquid butadiene rubber (LBR-305, Kuraray) and center-functionalized liquid butadiene rubber (C-LqBR), polymerized by anionic polymerization. In addition to the liquid butadiene rubbers, p-tert-octylphenol (P-Resin) and C5 hydrocarbon (H-Resin) tackifier resins, which can induce entanglement of rubber compounds, were researched as a processing aid to solve the bleeding problem. Liquid butadiene rubbers have significantly reduced extraction loss by crosslinking with the main rubber chain. They have also increased the abrasion resistance and showed similar or better mechanical and dynamical properties against HA oils. However, resin compounds did not show differences in extraction loss compared to HA oil compounds; instead, they showed increased wet traction.

**Keywords:** tire, processing aids, liquid rubber, resin, bleeding

### Introduction

Tire tread is the designed for key properties of tire which are fuel efficiency, abrasion resistance and wet grip performance. Furthermore, tire tread mainly provides contact area between road surface and tire. Styrene butadiene rubber (SBR) is the most commonly used rubber for tire tread.<sup>1</sup> The purpose of developing SBR compound for the tire tread is the achieve excellent mechanical and physical properties for using various application regions and long term. However, under the thermal, mechanical degradation and using for long term, the properties of tire tread decrease.<sup>2–8</sup> This degradation of tread compound can makes the product softened or hardened depend on the conditions.<sup>4–6</sup> The most common reason why properties of tire tread decrease is the processing oils which obtained from petroleum crude.

Processing oils are the one of key additives at rubber compound which can reduce the cost, increase processability, save energy and increase the filler dispersion. However, this processing oils can often evaporate or bleed from rubber compound that can decrease the rubber properties. Further-

more, these bleedings can be harmful for environment.<sup>9</sup> Highly aromatic oils are most commonly used processing oils for tire industry owing to their compatibility. And, the among of highly aromatic oils, Treated Distillate Aromatic Extract (TDAE) is the more preferred oil because of its high compatibility with SBR.<sup>10–11</sup> In order to increase tire life, the HA oils must be replaced by different processing aids which can keep the properties of tire for long term.

Research study which has recently reported shows, using liquid rubbers as a processing aid provides sufficient mechanical properties and maintain for long term at SBR based compound, which determined by extraction test.<sup>12</sup> Liquid rubbers are low molecular weight processing aids which have appreciable viscous flow at room temperature. They can be crosslinked with the main rubber chain during the vulcanization process.<sup>13</sup> Liquid rubbers can be polymerized by using living anionic polymerization techniques which have great superiorities such as allows to control microstructure like vinyl content and also capable to indicates low polydispersity index (PDI). When used the liquid rubber as a processing aid, these controllable properties have a major impact on determining the general characteristics of rubber compound.

One of important property of liquid rubbers is, it can cus-

<sup>†</sup>Corresponding author E-mail: [whkim@pusan.ac.kr](mailto:whkim@pusan.ac.kr)

tomize by functionalization by living chain termination.<sup>14</sup> After commercially introduced that silane-terminated liquid polybutadienes are used as a silane functionalized low molecular weight processing aid for tire technology, it has well reported at previous researches.<sup>15-19</sup> These functional groups based on silane technology are capable to provide same reaction structure as coupling agents.

Resins are another low molecular weight processing aid with high glass transition temperatures which are commonly used in tire industry because of good compatibility with tire elastomers.<sup>20</sup> And some of them called as tackifiers which build a tack between layers of green tire at uncured stage and assembling process. Tack is related with existing of movable chain ends which are merge at room temperature under small pressure and show resistance to stress if an attempt to separate layers again. This tack may also affect viscoelastic properties of rubber compound.<sup>21-24</sup>

In this study as a liquid rubber non-functionalized polybutadiene (N-LqBR), center functionalized polybutadiene (C-LqBR); as a resin *p*-tert-octylphenolic resin (P-Resin) and C5 hydrocarbon resin (H-Resin) have used to find solution for bleeding of processing oils from tire tread. Furthermore, properties of tire compound such as vulcanizate structure, mechanical properties, viscoelastic properties and abrasion resistances were also evaluated.

## Experimental

### 1. Materials

#### 1.1. Polymerization

The materials which used for polymerization are cyclohexane (99%, Samchun chemical Co.) as solvent, *n*-butyllithium as an initiator (2.0 mol/L in cyclohexane, Sigma Aldrich), 1,3-butadiene (Kumho Petrochemical Co.) as a monomer, anisole (99%, Samchun chemical Co.) as a modifier, for coupling agent tetraethyl orthosilicate (TEOS) (98%,

Sigma-Aldrich). And benzyl alcohol (Junsei, guaranteed reagent) was used as a termination agent.

#### 1.2. Compounding

Materials which used in this study; SSBR 5220M (Kumho Petrochemical Co., styrene content: 26.5 wt%, vinyl content: 26 wt%, non-oil extended), silica (Ultrasil 7000GR, Evonik), bis-[3-(triethoxysilyl)-propyl]-tetrasulfide (TESPT) as silane coupling agent. As a processing oil; treated distillate aromatic extracted (TDAE,  $T_g$ : -48°C), center functionalized liquid butadiene rubber (C-LqBR,  $T_g$ : -93°C), non-functionalized liquid butadiene rubber (N-LqBR “LBR-305, Kuraray”,  $T_g$ : -95°C), alkyl phenolic resin (P-Resin “*p*-tert-octylphenol”, softening point 95°C~100°C,  $T_g$ : 56°C KORESIN), hydrocarbon resin (H-Resin “C5”, softening point 95.8°C,  $T_g$ : 58°C) were used. Other additives include zinc oxide (ZnO), steric acid ( $\text{CH}_3(\text{CH}_2)_{16}\text{COOH}$ ), antioxidant *N*-(1,3-dimethyl butyl)-*N*-phenyl-*p*-phenylenediamine (6PPD) was used in the compound. Sulfur, *n*-cyclohexyl benzothiazyl-2-sulfenamide (CBS) and 1,3-diphenylguanidine (DPG) were used as vulcanization agents. Table 1 shows the information about processing aids.

#### 1.3. Polymerization of C-LqBR

Center functionalized liquid butadiene rubber (C-LqBR) was polymerized by anionic polymerization at 50°C. For polymerization the C-LqBR, at first, non-functionalized liquid butadiene rubber was polymerized by anionic polymerization at 50°C by adding cyclohexane, anisole, 1,3 butadiene and *n*-butyllithium to reactor. The amount of *N*-butyllithium (initiator) was used to control molecular weight of liquid butadiene rubber. Hereupon, TEOS diluted with cyclohexane added to synthesize C-LqBR. Lastly, benzyl alcohol added to terminate polymerization reaction.

#### 1.4. Manufacture of compounds and vulcanizates

#### 1.5. Mixing procedure

**Table 1.** Properties of Processing Aids

Properties	TDAE	N-LqBR (Kuraray)	C-LqBR	H-Resin (C-5)	P-Resin ( <i>p</i> -tert-octylphenol)
$M_n$ (g/mol)	-	26,000	24,000	-	-
$M_w$ (g/mol)	600	-	-	2,800	2,000
PDI	-	1.08	1.1	-	-
Vinyl content wt%	-	10	14	-	-
$T_g$ (°C)	-48	-95	-93	58	56

**Table 2.** Compound Formulation

		Ref.	N-LqBR	C-LqBR	P-Resin	H-Resin
Stage 1	SSBR (5220M)	100	100	100	100	100
	Silica (7000GR)	100	100	100	100	100
	TESPT	8	8	8	8	8
	TDAE oil	30	0	0	0	0
	LBR305	0	30	0	0	0
	PNU C-LqBR	0	0	30	0	0
	PTOP	0	0	0	30	0
	C5	0	0	0	0	30
	DPG			1.26		
	ZnO			3		
	S/A			2		
	6PPD			1		
Stage 2	Sulfur			0.75		
	CBS			2.2		
	ZBEC			0.2		

**Table 3.** Mixing Procedure

	Time	Action	rpm
Stage 1	0-40"	Rubber mixing	20
	40" - 1' 40"	Silica ½ + Silane ½ + DPG ½ + Oil ½	40
	1' 40" - 2' 40"	Silica ½ + Silane ½ + DPG ½ + Oil ½	40
	2' 40" - 7' 40"	Add ZnO, Stearic acid, 6PPD	50
		Dump at 150°C~155°C	
Stage 2	0 - 20"	Add master batch from 1 <sup>st</sup> stage	20
	20" - 2'	Add curatives	40
		Dump at 60°C~70°C	40

Compounds were prepared using an internal mixer (kneader, 300 mL) based on the formulation shown in Table 2. The mixing procedure is shown in Table 3. The dump temperature was set at 150°C~155°C and the filler factor was set at 70% of the mixer capacity. The input unit was administered on a rubber basis with the parts per hundred rubber (phr). For 2nd stage, masterbatches from 1st stage had been mixed with curatives at 50°C initial temperature.

## 2. Measurements

### 2.1. Characterization of C-LqBR

<sup>1</sup>H-Nuclear magnetic resonance spectroscopy (<sup>1</sup>H NMR; Varian, Unity Plus 300 spectrometer, Garden State Scientific, USA) was used to determine the vinyl content and functional groups in liquid butadiene rubber.

Molecular weight and molecular weight distribution were

measured by gel permeation chromatography (GPC, Shimadzu, Japan). GPC was measured using solvent delivery unit, reflective index detector and three types of column (Stryagel column (HT 6E, 10 µm, 7.8 mm × 300 mm), styragel column (HMW 7, 1520 µm, 7.8 mm × 300 mm) and styragel column (HMW 6E, 1520 µm, 7.8 mm × 300 mm). Calibration of GPC were prepared by using polystyrene standard.

### 2.2. Payne effect

Storage modulus was measured by the rubber process analyzer 2000 (RPA 2000) from Alpha Technologies (Hudson, OH, USA) at 60°C and between 0.28%~40.04% strain range.

### 2.3. Mooney viscosity

Processability of rubber was evaluated by Mooney viscometer (Vluchem IND, Korea) according to ASTM D1646

at 100°C and 2 rpm rotor speed. (ML<sub>1+4</sub>@100°C)

## 2.4. Cure characteristics

Compound cure characteristic was measured by moving die rheometer (MDR, ALR-3, TOYOSEIKI, Japan) under 160°C for 30 mins at oscillation angle of  $\pm 1^\circ$  to determine optimized vulcanization time.

## 2.5. Solvent extraction and crosslink density

Vulcanizates samples were prepared in 10 mm  $\times$  10 mm  $\times$  2 mm sizes and immersed to 30 mL THF for two days then, 30 mL hexane for 1 days to determine organic extraction mass. After drying at the room temperature for 1 day weight loss gives organic extraction loss. Hereafter, the samples were immersed to toluene for 24 hours and weighed again to determine crosslink density. Crosslink density was calculated by using Flory-Rehner equation (1).

$$V = \frac{1}{2M_c} = - \frac{\ln(1-V_r) + V_r + \chi V_r^2}{2\rho_r V_0 \left( V_r^{1/3} - \frac{V_r}{2} \right)} \quad (1)$$

$V$  : Crosslink density (mol/g)

$M_c$ : average molecular weight between crosslink points (g/mol)

$V_r$  : the volume fraction of rubber in the swollen gel at equilibrium

$V_s$  : the molar volume of solvent (cm<sup>3</sup>/mol)

$\rho$  : the density of the rubber sample (g/cm<sup>3</sup>)

$\chi$  : the polymer-solvent interaction parameter

$V_r$  value at the Flory-Rehner Equation was obtained from the equation (2)

$$V_r = \frac{\frac{W_d - W_f}{\rho_r}}{\frac{W_d - W_f}{\rho_r} + \frac{W_s - W_d}{\rho_s}}$$

$W_d$ : Weight of dried sample after swelling

$W_f$ : Weight of filler in sample

$W_s$ : Weight of sample after swelling

$\rho_s$  : Solvent density

$\rho_r$  : Rubber density

## 2.6. Mechanical properties

Mechanical properties which are tensile strength, elongation at break and the modulus were tested by universal testing

machine (UTM, Model: KSU-05M-C, KSU Co, Korea). Specimens were prepared according to ASTM D412 which is 100 mm  $\times$  25 mm  $\times$  2 mm sized.

## 2.7. Abrasion loss

Abrasion resistance was measured by Deutsche Industrie Normen (DIN, 53516) wear tester machine. The samples which were used had made into a cylinder sizes 16 mm  $\times$  8 mm. Samples are weighed before and after testing on emery cloth then calculated to abrasion loss.


## 2.8. Dynamic viscoelastic properties

Dynamic viscoelastic properties were measured by strain-controlled rheometer (ARES-G2, TA Instrument) at -60°C to 70°C, frequency of 10 Hz, 0.5% strain and solid torsion mode.


# Results and Discussion

## 1. Characterization of C-LqBR


Reaction mechanism of C-LqBR which explained in Figure 1 shows that it is possible to make four different type functionalized liquid butadiene.<sup>25</sup> Molecular weight and molecular weight distribution were determined by GPC and shown in Figure 2. Determination has done at two steps. First, during the polymerization, the sample (aliquot) had been taken before adding coupling agent and measured the

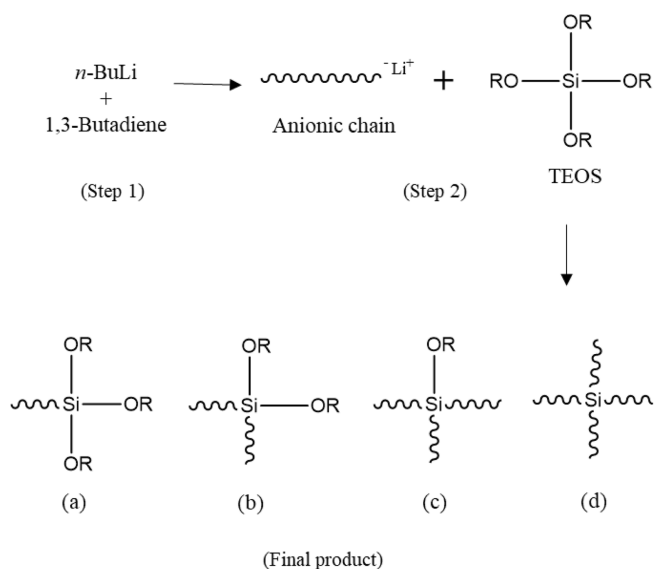

**Figure 1.** Polymerization mechanism of center functionalized liquid butadiene (C-LqBR)

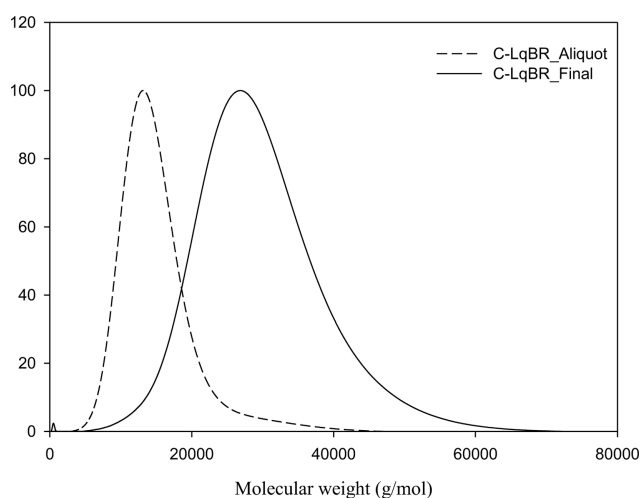

**Figure 2.** GPC curve of center functionalized liquid butadiene (C-LqBR).

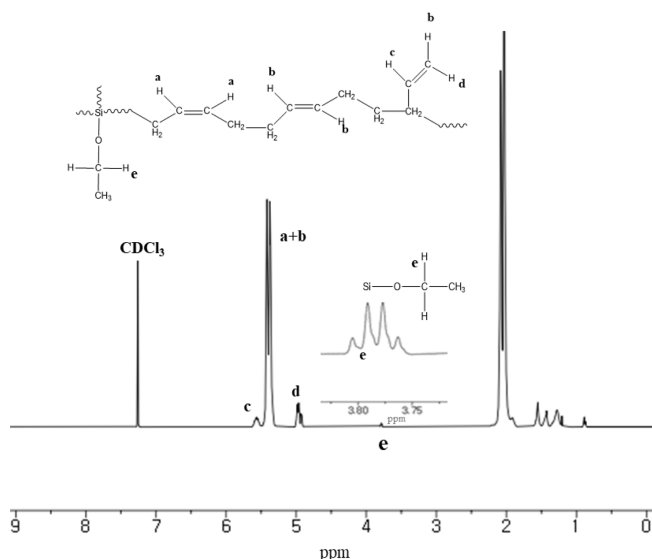

**Figure 3.** Nuclear magnetic resonance spectrometer ( $^1\text{H}$ -NMR) peaks of center functionalized liquid butadiene (C-LqBR).

molecular weight and then after adding coupling agent another sample (final) had been taken to determine molecular weight. Determination of those two samples are shown in Table 4. Increasing molecular weight to two times verify us polymerization reaction is prone to create final product (b) in Figure 1. Additionally, microstructure of C-LqBR was


**Table 4.** Characteristics of Center Functionalized Liquid Butadiene Rubber (C-LqBR)

	Aliquot	Final
Mn (g/mol)	12,000	24,000
PDI	1.1	1.1
Vinyl content (%)	-	14


determined by  $^1\text{H}$ -NMR and shown in Figure 3. Liquid polybutadiene contains 1,2 vinyl group which showed peak at 4.2~5.1 (d) and 1,4 addition of polybutadiene at 5.1~5.7 (c). Considering the peaks in Figure 3 the vinyl content in final C-LqBR have calculated as 14%. Also, ethoxy peaks at 3.75~3.80 (e) from Figure 3 verify C-LqBR successfully functionalized.

## 2. Payne effect

Payne effect can describe as the difference of storage modulus ( $G'$ ) at low and high strains which represents dispersion of silica in rubber compounds.<sup>26</sup> Usually, high difference of storage modulus between high strain and low strain shows strong filler-filler interaction.<sup>27</sup> In this study, the storage modulus was measured by the rubber process analyzer 2000

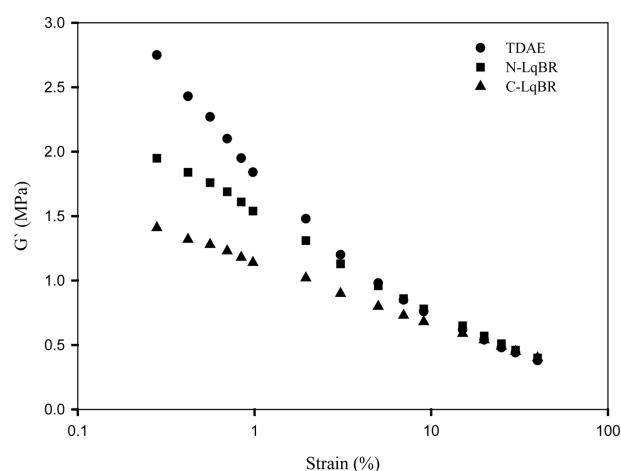

**Figure 4.** The shear storage modulus ( $G'$ ) of liquid butadiene compounds compare to TDAE compound.

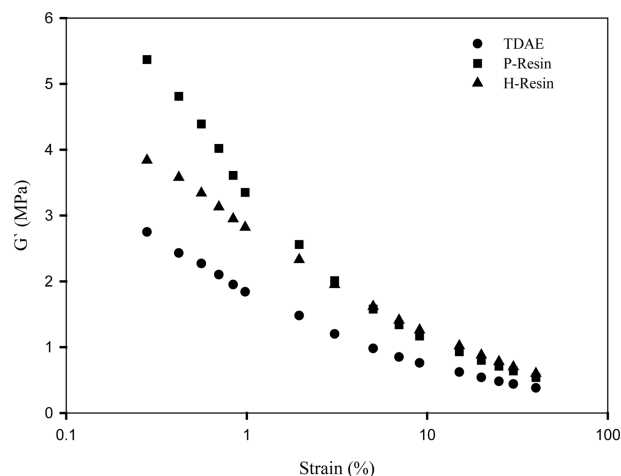

**Figure 5.** The shear storage modulus ( $G'$ ) of resin compounds compare to TDAE compound.

**Table 5.** Storage Modulus Differences between Large and Small Strain



Compound	TDAE	N-LqBR	C-LqBR	P-Resin	H-Resin
$\Delta G'$ (MPa) (0.28%-40.04%)	2.37	1.55	1.01	4.83	3.24

(RPA 2000) from Alpha Technologies (Hudson, OH, USA) at 60°C and shown in Figure 4&5. Table 5 shows  $\Delta G'$  value of compounds. N-LqBR and C-LqBR compounds are showing lower  $\Delta G'$  value than TDAE compound. Processing oils are the lubricants which are basically lowering the intermolecular interactions. However, liquid butadiene rubbers and main polymer of compound (SBR) have similar structure which increase the possibility of lubrication. Liquid butadiene rubbers can also improve the silica dispersion due to the increased viscosity compared to TDAE oil. Furthermore, ethoxy groups of C-LqBR can react with the silanol groups on silica surface and reduce the polarity of silica, which improves the dispersion of silica. Thus C-LqBR compound shows lower  $\Delta G'$  value than N-LqBR compound.

In the case of resin including compounds, they show higher  $\Delta G'$  value than TDAE compound. Resins that we have used in our research are solid materials when the temperature below 95°C~100°C and the temperature of test condition of RPA is 60°C, thus, resin compounds show high  $G'$  values at low strain.<sup>28</sup> Besides, -OH group of phenolic resin forms hydrogen bond network.<sup>29</sup> When the filler dispersed in the rubber, it forms weak chemical interaction between filler particles. This filler-filler network can be broken under the strain. But in the case of P-Resin, -OH groups additionally form hydrogen bonds with the silica surface and increase storage modulus at low strain. This property of P-Resin may cause to high storage modulus than H-Resin.

### 3. Cure characteristics and Mooney viscosity

Cure characteristics which were measured by moving die rheometer are shown in Figures 6 and 7.  $\Delta T$  ( $T_{\max} - T_{\min}$ ) has described difference between maximum torque and minimum torque, and  $\Delta T$  is very commonly related to crosslink density, which means high  $\Delta T$  indicates high crosslink density.<sup>30</sup> However, ethoxy groups of C-LqBR can react with the silanol groups on silica surface and increases the filler rubber interaction, which increases  $\Delta T$  of rubber. H-Resin used compound has similar  $\Delta T$  value as a TDAE compound which doesn't show crosslink reaction from the MDR data on the

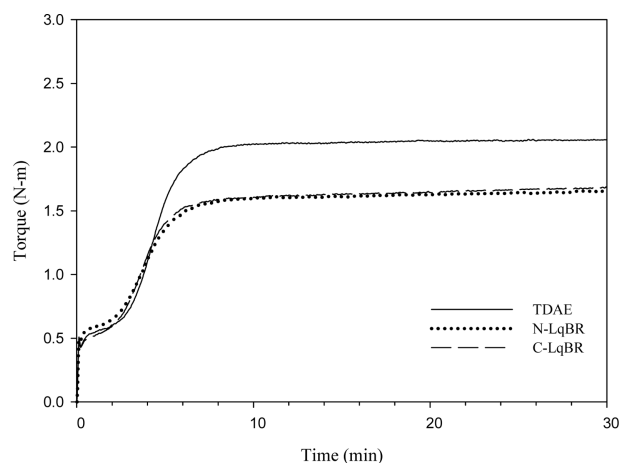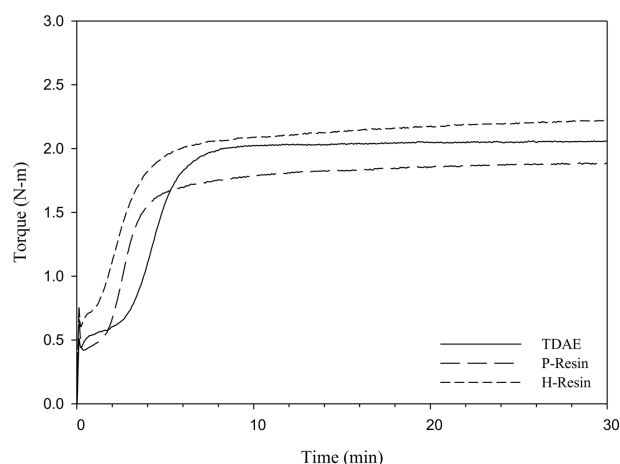**Figure 6.** Cure characteristics of liquid butadiene compounds.**Figure 7.** Cure characteristics of resin compounds.

other side P-Resin used compound shows lower  $\Delta T$  than TDAE compound. P-Resin and H-Resin are the tackifiers which provide tack at uncured stage. Tacky stocks often cause air entrapment in the building process which can lead to cure defects.<sup>31</sup> In the case of phenolic resin polar-polar interaction between polar accelerators and polar group of phenolic resin cause the partial loss of accelerators and decreases the cured properties.

From the molecular weight difference between TDAE oil and liquid butadiene rubbers we can expect that liquid butadiene rubber used compounds may have higher Mooney viscosity. Table 6 shows that, liquid butadiene rubbers show similar Mooney viscosity as TDAE oil; even though, liquid butadiene rubbers have higher molecular weight than the TDAE oil, structure similarity between liquid butadiene rubbers and SBR increases the lubrication and lower the Mooney viscosity. Although resins have not so higher molecular weight than TDAE oil, they have higher Mooney vis-



**Table 6.** Cure Characteristics and Mooney Viscosity of Compounds



Compound	Mooney viscosity ( $ML_{1+4}@100^{\circ}C$ )	$T_{min}$ (N-m)	$T_{max}$ (N-m)	$\Delta T$ (N-m)	$t_{10}$ (min:s)	$t_{90}$ (min:s)
TDAE	108	0.44	2.06	1.62	01:58	06:34
N-LqBR	106	0.48	1.66	1.18	01:10	06:51
C-LqBR	108	0.42	1.69	1.27	01:32	06:51
P-Resin	134	0.42	1.89	1.47	01:43	07:21
H-Resin	Over range	0.60	2.22	1.62	01:06	07:49

cosity than TDAE oil compound. Resins have high softening point which is between  $95^{\circ}C$ – $100^{\circ}C$ ; test condition of Mooney viscosity is ( $100^{\circ}C$ ), not enough to heat the resins. Thus, resin compounds have higher Mooney viscosity.

#### 4. Crosslink density and solvent extraction

There are two factors which affect the crosslink density of vulcanizate rubber; filler-rubber interactions and chemical crosslinks.<sup>32</sup> The sum of these two factors can be defined as a total crosslink density. During the vulcanization, the liquid butadiene rubbers consume sulfur which decreases the crosslink density of rubber compound. This is the reason why N-LqBR and C-LqBR compounds have less crosslink density. Figure 8 shows the crosslink density of C-LqBR compound increases with functional groups. Ethoxy groups of C-LqBR react with the silanol group on silica surface and it increases the filler rubber interaction which effects crosslink density. In the case of resin compounds, H-Resin compound shows similar crosslink density as the TDAE compound; unlike H-Resin compound, P-Resin compound has less crosslink density because of the partial loss of accelerators.

It has known that TDAE oil has bleeding problem from the rubber compound which decreases the properties. The extraction test verified crosslink reaction between liquid

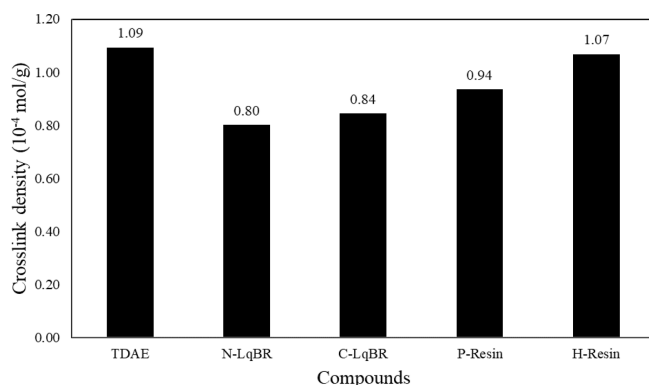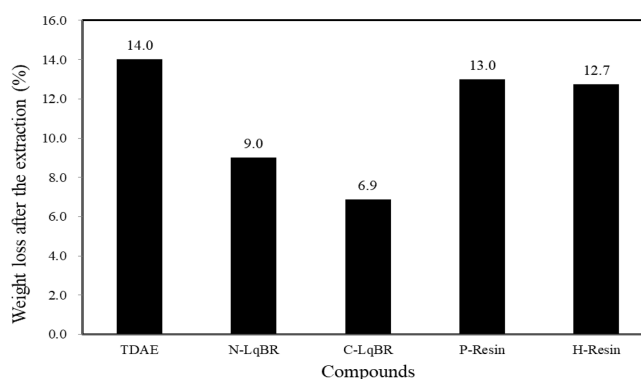**Figure 8.** Crosslink density of rubber compounds.**Figure 9.** Weight loss of rubber compounds after extraction.

butadiene rubbers and SBR which prevents the bleeding in compounds as shown in Figure 9. Extraction loss difference between liquid butadiene rubbers, caused by the silanization reaction of functional groups of C-LqBR. Unless the liquid butadiene rubbers, resins show similar crosslink density value as TDAE oil which means they don't have crosslink reaction with main rubber. Thus, resin compounds have similar weight loss as TDAE oil compound.

#### 5. Mechanical properties and DIN abrasion loss

The mechanical properties of compounds which measured by universal testing machine and DIN abrasion loss values are shown in Figure 10&11 and Table 7. Usually, mechanical properties and crosslink density of the compounds show similar behavior.<sup>33</sup> And modulus at 300% elongation ( $M_{300\%}$ ) is most commonly related with filler rubber interaction.<sup>34</sup> Liquid butadiene rubber compounds show lower modulus at  $M_{300\%}$  than TDAE oil compound as expected from crosslink density. However, unlike the liquid butadiene rubber compounds, resin compounds show different trends. Although, the H-Resin compound has similar crosslink density as TDAE compound, when comparing the cure characteristics and mechanical properties of H-Resin, it can be seen that  $T_{max}$  and  $M_{300\%}$  values of H-Resin compound higher than the

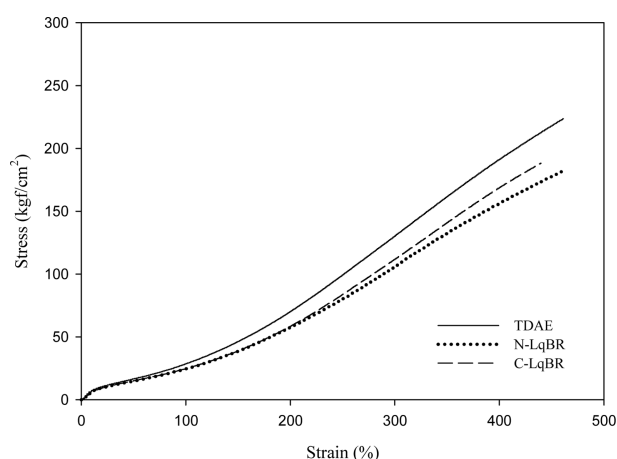


Figure 10. Mechanical properties of liquid butadiene compounds.

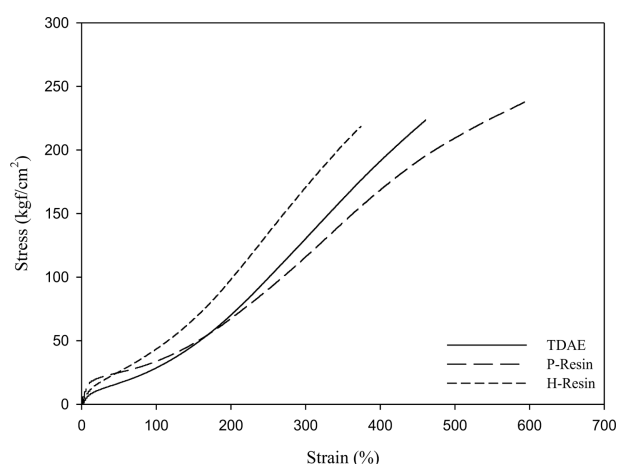


Figure 11. Mechanical properties of resin compounds.

Table 7. Mechanical Properties of Compounds

Compound	$M_{100\%}$ (kgf/cm <sup>2</sup> )	$M_{300\%}$ (kgf/cm <sup>2</sup> )	Elongation at break (%)	Tensile strength (kgf/cm <sup>2</sup> )	DIN abrasion loss (mg)	$T_g$ (°C)
TDAE	29	132	459	225	81	-35
N-LqBR	25	106	463	183	74	-43
C-LqBR	25	112	440	188	71	-43
P-Resin	34	116	595	238	144	-29
H-Resin	43	170	375	218	114	-27

TDAE oil compound. This may be caused by characteristics of H-Resin. Furthermore, due to partial loss of accelerator effect from cure state and less crosslink density in Figure 8 resulted as low mechanical property for P-Resin compound.

Commonly abrasion loss increases with increasing glassy transition temperature<sup>35</sup>; resin compounds have higher  $T_g$  than the other compounds that caused higher abrasion loss. Between two resin compounds, H-Resin compound has higher crosslink density which decreases abrasion loss. Thus, H-Resin compound has better abrasion resistance than P-Resin compound.<sup>34</sup> LqBRs have much lower  $T_g$  than the TDAE oil and resins which resulted as less abrasion loss. Furthermore, the reason why C-LqBR has better abrasion resistance than N-LqBR is caused from higher crosslink density.

## 6. Dynamic viscoelastic properties

Results of dynamic viscoelastic properties are shown in Figure 12&13 and Table 8. Dynamic viscoelastic properties are mostly related with the tire performance. Loss modulus ( $G''$ ) is a loss factor at low temperature conditions (0°C-20°C) which indicates the wet traction; higher value of  $G''$


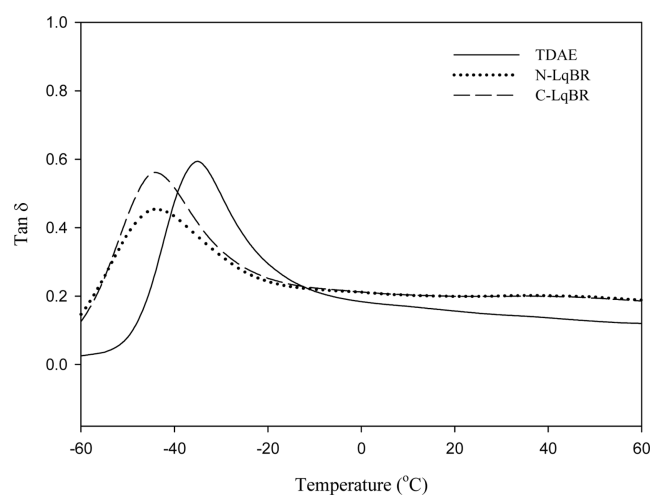


Figure 12. Tan  $\delta$  curves of the vulcanizates dependent on the temperature; liquid butadiene rubber compounds.

higher the wet traction.<sup>36</sup> During the repeated deformation, the energy applied to rubber is converted into heat as the result of destruction and regeneration of filler networks, because of this, the temperature of rolling tire rises up to 60-80°C. So, Tan  $\delta$  at 60°C can represent rolling resistance of tire.<sup>37</sup> Hysteresis has been known the main reason of energy loss in tire tread compound.<sup>38</sup> Table 8 verify the N-LqBR and



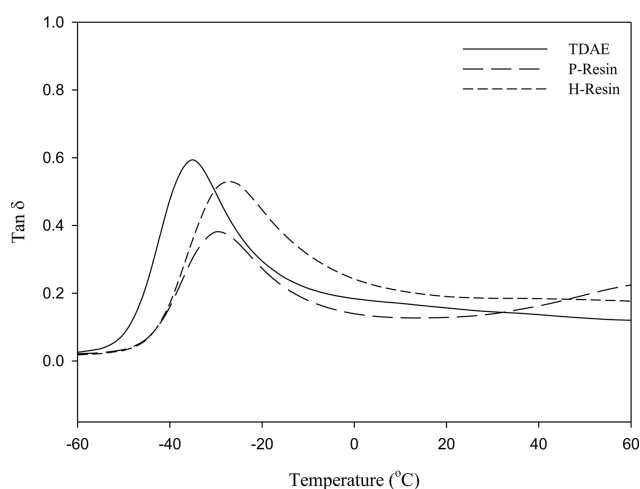


**Figure 13.** Tan  $\delta$  curves of the vulcanizates dependent on the temperature; resin compounds.

C-LqBR compounds with free chain ends which are visualized in Figure 14, have higher rolling resistance which cause the hysteresis at compound compare to TDAE compound.

Another main reason which causes the hysteresis is filler dispersion; the filler-filler network is relatively weak and breaks easily under the influence strain which causes energy losses, that means better filler dispersion better rolling resistance.<sup>39</sup> From the Payne effect results; resin compounds have high filler-filler interaction, bad dispersion which cause higher rolling resistance than the other compounds.

Resins are processing aids which have high glass transition temperature ( $T_g$ ). Higher  $T_g$  of resin at Table 8 can higher  $T_g$  of rubber compound and increases the energy dissipation, thus resin compounds have higher wet traction.<sup>40,41</sup> Incompatible resin forms secondary peak in the range of the resin  $T_g$  in the vulcanizates as it can be seen in Figure 13. So, this poor compatibility resin forms separated phase at compound. Phase separation can increase the hysteresis and cause the bad rolling resistance at resin compound.<sup>20</sup> This effect can be seen at P-Resin compound.

It has indicated that softer compounds with higher resili-

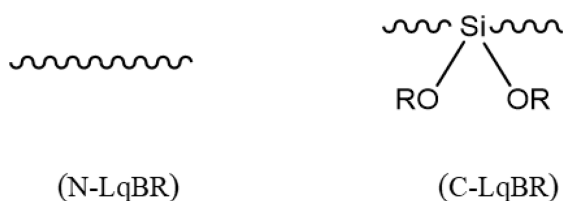

**Figure 14.** Liquid butadiene rubber structures.

**Table 8.** Viscoelastic Properties of Vulcanizates from Liquid Butadiene Rubber and Resin Compounds

Compound	Snow traction	Rolling resistance	Wet traction
	$G'@-30^{\circ}\text{C}$ (MPa)	$\tan \delta$ $60^{\circ}\text{C}$	$G''@0^{\circ}\text{C}$ (MPa)
Ref.	130	0.120	6.6
LqBR	67	0.188	5.2
C-LqBR	54	0.185	4.4
P-Resin	446	0.224	17
H-Resin	396	0.176	11.4

ence, had higher friction on ice road in the temperature range of  $-30^{\circ}\text{C}$  to  $0^{\circ}\text{C}$ . The rubber compounds with low  $T_g$  were recommended for the best traction performance of tread compounds on ice and snow road.<sup>42</sup> Table 8 shows that liquid butadiene rubbers have lowest storage modulus ( $G'$ ) values which indicates snow traction, because of their low  $T_g$  properties. Also, at the low temperatures processing oils can migrate or bleed out from the rubber; so, tire tread gets stiffer and low temperature performance decreases.<sup>9</sup> Liquid butadiene rubbers crosslink the main polymer, prevent the extraction loss.

## Conclusion

In this study different type processing aids were used to reduce migration and evaluate the physical properties of SSBR/silica compounds. Two different type of liquid butadiene rubbers and two different resins were applied. Solvent extraction test showed excellent results that crosslinkable liquid butadiene rubbers reduce extraction loss from the compounds. Liquid butadiene rubbers not only reduce the extraction but also increase abrasion resistance and filler dispersion. Furthermore, liquid butadiene rubbers keep elasticity properties of tire and provide long life time at low temperature conditions which is important for snow tire.

Resins are processing aids with high glass transition temperature which can also called as a tackifier. Tack is related with easily movable chain ends that occurs, entanglement under small pressure to resist separation at rubber compound but unlike the liquid butadiene rubber compounds, resin compounds do not show chemical interaction. Compared to TDAE compound, they have shown similar extraction and crosslink density results. High  $T_g$  of resin increased abrasion loss but resin compounds showed better wet traction than the TDAE compound.

## Acknowledgments

This work was supported from Minister of Trade, Industry and Energy Grant funded by Korean Government [Project Number 20010851], Republic of Korea.

## References

1. A. Petchkaew, "Implications of non-carcinogenic pah-free extender oils in natural rubber-based tire compounds" Enschede, University of Twente, (2015).
2. W. Schnabel, "Polymer degradation, principles and practical applications", *Hanser Munchen*, **87**, 838 (1983).
3. Li, G. Yang, and J. L. Koenig, "A review of rubber oxidation", *Rubber Chem. Technol.*, **78**, 355 (2005).
4. T. Nakazono, A. Ozaki, and A. Matsumoto, "Phase separation and thermal aging behavior of styrene-butadiene rubber vulcanizates using liquid polymers as plasticizers studied by differential scanning calorimetry and dynamic mechanical spectroscopy", *J. Appl. Polym. Sci.*, **120**, 434 (2010).
5. A. Ahagon, M. Kida, and H. Kaidou, "Aging of tire parts during service. I. Types of aging in heavy-duty tires", *Rubber Chem. Technol.*, **63**, 683 (1990).
6. H. Kaidou and A. Asahiro, "Aging of tire parts during service. II. Aging of belt-skim rubbers in passenger tires", *Rubber Chem. Technol.*, **63**, 698 (1990).
7. A. Santoso, U. Giese, and R. H. Schuster, "Investigations on initial stage of aging of tire rubbers by chemiluminescence spectroscopy", *Rubber Chem. Technol.*, **80**, 762 (2007).
8. K. R. J. Ellwood, J. Baldwin, and D. R. Bauer, "Numerical simulation of thermal oxidation in automotive tires", *Rubber Chem. Technol.*, **79**, 249 (2006).
9. J. K. Hirata, S. Kuhawara, B. K. Chapman, and D. Kilian, "Effects of crosslinkable plasticizers", *RFP International*, **6**, 212 (2011).
10. The Swedish National Chemicals Inspectorate, "HA oil in automotives tyres", *KEMI Reports*, (2003).
11. A. Petchkaew, K. Sahakaro, and J. Noordermeer, "Petroleum-based safe process oils in NR, SBR and their blends: study on unfilled compounds part II properties", *Kautsch. Gummi Kunstst.*, **66**, 21 (2013).
12. T. Nakazono and A. Matsumoto, "Mechanical properties and thermal aging behavior of styrene-butadiene rubbers vulcanized using liquid diene polymers as the plasticizer", *J. Appl. Polym. Sci.*, **118**, 2314 (2010).
13. S. Fabien and K. H. Steven, "Silane-terminated liquid poly-(butadienes) in tread formulations: a mechanistic study", *Rubber Chem. Technol.*, (2020). <https://doi.org/10.5254/rct.20.80359>
14. D. French, "Functionally terminated butadiene polymers", *Rubber Chem. Technol.*, **42**, 71 (1969).
15. Cray Valley, Technical Data Sheet, Ricon 603, (2017), <http://www.crayvalley.com/docs/tds/ricon-603-.pdf?sfvrsn%42>.
16. Evonik, "Less fuel and lower CO<sub>2</sub> emissions with POLY-VEST® ST Tires", (2017), [https://corporate.evonik.com/en/media/press\\_releases/Pages/article.aspx?articleId%4100233](https://corporate.evonik.com/en/media/press_releases/Pages/article.aspx?articleId%4100233).
17. R. Herpich, Bayer Corp., U.S. Patent 0,082,333 (2002).
18. H. Takuya, Sumitomo Rubber Ind., J. Patent 2,005,146,115 (2003).
19. S. Satoyuki, Yokohama Rubber Co. Ltd., J. Patent 2,005,350,603 (2005).
20. M. T. Arigo, "Using Impera performance resins to expand the magic triangle for tire tread compounds", *Rubber World*, **25**, 260 (2019).
21. M. Sherriff, R. W. Knibbs, and P. G. Langley, "Mechanism for the action of tackifying resins in pressure-sensitive adhesives", *J. Appl. Polym. Sci.*, **17**, 2423 (1973).
22. D. W. Aubrey and M. Sherriff, "Viscoelasticity of rubber-resin mixtures", *J. Polym. Sci., Polym. Chem. Ed.*, **16**, 2631 (1978).
23. D. W. Aubrey and M. Sherriff, "Peel adhesion and viscoelasticity of rubber-resin blends", *J. Polym. Sci., Polym. Chem. Ed.*, **18**, 2597 (1980).
24. F. W. Barlow, "Rubber Compounding: Principles, Materials, and Techniques", ed. by Marcel Dekker, Inc., p.209, Newyork, (1988).
25. B. Seo, K. Kim, and H. Lee, "Effect of styrene-butadiene rubber with different macrostructures and functional groups on the dispersion of silica in the compounds", *Macromol. Res.*, **23**, 4663 (2015).
26. A. R. Payne, "The dynamic properties of carbon black loaded natural rubber vulcanizates. Part II", *J. Appl. Polym. Sci.*, **6**, 57 (1962).
27. C. G. Robertson, "Flocculation in elastomeric polymers containing nanoparticles: Jamming and the new concept of fictive dynamic strain", *Rubber Chem. Technol.*, **88**, 463 (2015).
28. W. Thaijaroen, "Effect of tackifiers on mechanical and dynamic properties of carbon-black-filled NR vulcanizates", *Polymer Engineering & Science* **51**, 2465 (2011).
29. G. R. Hamed, "Tack and Green Strength of Elastomeric Materials", *Rubber Chem. Technol.*, **54**, 576 (1981).
30. S. Choi, "Improvement of properties of silica-filled natural rubber compounds using polychloroprene", *J. Appl. Polym. Sci.*, **83**, 2609 (2002).
31. K. Kumar, "Influence of tackifiers and nanoclays on autohesive tack of brominated isobutylene-co-p-methylstyrene elastomer", Diss. IIT Kharagpur, (2010).
32. J. Lee, N. Park, S. Lim, B. Ahn, W. Kim, H. Moon, H. Paik, and W. Kim, "Influence of the silanes on the crosslink density and crosslink structure of silica-filled solution styrene butadi-

- ene rubber compounds”, *Compos. Interface.*, **24**, 711 (2017).
33. K. Hwang, H. Mun, and W. Kim, “Effect of Reversible Addition-Fragmentation Transfer Emulsion Styrene Butadiene Rubber (RAFT ESB) on the Properties of Carbon Black-Filled Compounds”, *Polymer*, **12**, 933 (2020).
34. J. Lee, B. Ahn, W. Kim, H. Moon, H. Paik, and W. Kim, “The effect of accelerator contents on the vulcanizate structures of SSBR/silica vulcanizates”, *Compos. Interface.*, **24**, 563 (2017).
35. A.F. Halasa, J. Prentis, B. Hsu, and C. Jasiunas, “High vinly-higy styrene solution SBR”, *Polymer*, **46**, 4166 (2005).
36. S. Maghami, “Silica-Filled Tire Tread Compounds: An Investigation into the Viscoelastic Properties of the Rubber Compounds and Their Relation to Tire Performance”, Enschede, University of Twente, (2016).
37. B. Ahn, N. Park, D. Kim, and W. Kim, “Influence of end-functionalized solution styrene-butadiene rubber on silica-filled vulcanizates with various silica-silane systems”, *Rubber Chem. Technol.*, **92**, 364 (2019).
38. R. Bond and G. F. Morton, “A taylor-made polymer for tyre application”, *Polymer*, **25**, 132 (1984).
39. E. Cichomski, “Influence of Silica-Polymer Bond Microstructure on Tire-Performance Indicators”, *Kautsch. Gummi Kunstst.*, **68**, 38 (2015).
40. G. Heinrich, “The dynamics of tire tread compounds and their relationship to wet skid behavior”, *Phys. Polym Network*, **16**, 26 (1992).
41. G. Heinrich and H. B. Dulmer, “Wet skid properties of filled rubbers and the rubber-glass transition”, *Rubber Chem. Technol.*, **71**, 53 (1998).
42. F. Shingo, “Analysis of ice and snow traction of tread material”, *Rubber Chem. Technol.*, **69**, 648 (1996).